

---

---

विद्युत सम्पर्कों के लिए उच्च शुद्धता वाले सोने  
के तार — विशिष्टि  
( पहला पुनरीक्षण )

High Purity Gold Wire for Electrical  
Contacts — Specification  
( First Revision )

ICS 77.120.99

© BIS 2023



भारतीय मानक ब्यूरो  
BUREAU OF INDIAN STANDARDS  
मानक भवन, 9 बहादुर शाह ज़फर मार्ग, नई दिल्ली - 110002  
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG  
NEW DELHI - 110002  
[www.bis.gov.in](http://www.bis.gov.in) [www.standardsbis.in](http://www.standardsbis.in)

## FOREWORD

This Indian Standard (First Revision) was adopted by the Bureau of Indian Standards, after the draft finalized by the Precious Metals Sectional Committee, had been approved by the Metallurgical Engineering Division Council.

This standard was first published in 1978. This revision has been brought out to bring the standard in the latest style and format of the Indian Standards.

In addition, following significant changes have been made:

- a) Reference clause has been included; and
- b) Reference to IS 16901 has been provided in **4** for chemical testing.

High purity gold wire is used in various types of contacts for low and medium energy circuits in semiconductor devices. This standard lays down chemical composition and physical requirements of high purity gold, so that it may serve as suitable material for electrical contacts.

The composition of the Committee responsible for formulation of this standard is given in Annex B.

For the purpose of deciding whether a particular requirement of this standard is complied with, the final value, observed or calculated, expressing the result of a test or analysis, shall be rounded off in accordance with IS 2 : 2022 'Rules for rounding off numerical values (*second revision*)'. The number of significant places retained in the rounded off value should be the same as that of the specified in this standard.

*Indian Standard***HIGH PURITY GOLD WIRE FOR ELECTRICAL  
CONTACTS — SPECIFICATION***( First Revision )***1 SCOPE**

This standard specifies requirements for high purity gold wire used for electrical contacts.

**2 REFERENCES**

The standards given below contain provisions which, through reference in this standard, constitute provisions of this standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreement based on this standard are encouraged to investigate the possibility of applying the most recent edition of these standards:

<i>IS No.</i>	<i>Title</i>
IS 1387 : 1993	General requirements for the supply of metallurgical materials ( <i>second revision</i> )
IS 16901 : 2022/ ISO 15093 : 2020	Jewellery and precious metals — Determination of high purity gold, platinum and palladium — Difference method using ICP-OES ( <i>first revision</i> )

**3 SUPPLY OF MATERIAL**

**3.1** General requirements relating to the supply of material shall conform to IS 1387.

**3.2** The material shall be supplied either in annealed or in hard condition.

**4 CHEMICAL COMPOSITION**

When tested in accordance with IS 16901 the purity of gold shall be 99.99 percent minimum and the

impurities shall not exceed the limits as specified below:

<i>Sl No.</i>	<i>Constituents</i>	<i>Percent, Max</i>
(1)	(2)	(3)
i)	Copper	0.009
ii)	Silver	0.009
iii)	Any other metallic impurities, such as bismuth	0.003
iv)	Total of all metallic impurities including silver and copper	0.010

**5 FREEDOM FROM DEFECTS**

The surface of wire shall be clean and free from lubricants, oils, dirt when viewed under 30X magnification.

**6 DIMENSIONS**

**6.1** The wire shall have the following dimensions. If required, the wire may be annealed suitably before the measurement of dimensions:

<i>Sl No.</i>	<i>Diameter</i>	<i>Tolerance</i>
	mm	mm
(1)	(2)	(3)
i)	0.013	± 0.001
ii)	0.020	± 0.001
iii)	0.023	± 0.001
iv)	0.03	± 0.002
v)	0.05	± 0.002
vi)	0.08	± 0.003
vii)	0.13	± 0.004

**6.2** For measuring the average diameter, the method given in **6.2.1** shall be employed.

### 6.2.1 Procedure

Select a test specimen at least 1 m from the end of a spool or sufficiently far from either end to be free from bends, kinks or other damage resulting in lack of straightness of the cut length. The wire shall be drawn from the spool under a low even tension so that no elongation of the wire takes place.

**6.2.1.1** Cut each test specimen to a length of 200 mm  $\pm$  0.1 mm. To prevent stretching, care shall be taken so that the tension is just sufficient to eliminate the sag and curl.

**6.2.1.2** Fold the test specimen upon itself several times and twist to make a compact bundle with a loop consisting of a single strand for hanging it on the balance beam. In case the specimens are more than one, they shall be twisted together and hung by a loop consisting of a single strand. The specimen shall be handled as little as possible and the

operator's hands shall be cleaned and dried.

**6.2.1.3** Weigh in a micro-balance capable of reading up to 0.000 2 mg with an accuracy of 0.004 mg. Handle and use the balance as recommended by the manufacturer. Report average weight of the wire to three significant figures in mg/200 mm.

### 6.2.2 Calculation

$$\text{Diameter, mm} = \sqrt{\frac{M}{1.90}} \times 0.025$$

where

$M$  = mass, in mg, of 200 mm of wire.

NOTE — Density of gold is to be taken as 19.34 g/cm<sup>3</sup>.

## 7 TENSILE PROPERTIES

**7.1** The wire in annealed and hard condition shall meet the requirements given in Table 1 and Table 2 respectively when tested by methods given in **7.2** and **7.3**.

**Table 1 Elongation and Breaking Load for Annealed Wire**

(Clause 7.1)

SI No.	Diameter	Elongation Percent on Gauge Length of 200 mm	Breaking Load
	mm		g, Min
(1)	(2)	(3)	(4)
i)	0.013	1.0 to 3.0	1
ii)	0.020	1.0 to 8.0	3
iii)	0.023	1.0 to 8.0	4
iv)	0.03	1.0 to 12.0	5
v)	0.05	2.0 to 20.0	20
vi)	0.08	4.0 to 25.0	45
vii)	0.13	5.0 to 25.0	120

**Table 2 Elongation and Breaking Load for Head Wire**

(Clause 7.1)

SI No.	Diameter	Elongation Percent on Gauge Length of 200 mm	Breaking Load
	mm		g, Min
(1)	(2)	(3)	(4)
i)	0.013	0.5 to 1.5	3
ii)	0.020	0.5 to 2.0	8
iii)	0.023	0.5 to 2.0	13
iv)	0.03	0.5 to 2.5	17
v)	0.05	0.5 to 3.0	70
vi)	0.08	0.5 to 3.0	150
vii)	0.13	0.5 to 4.0	420

## 7.2 Procedure for Testing Tensile Properties

Cut a test piece which shall be 250 mm. Mark on the test piece, gauge length of 200 mm with an accuracy of  $\pm 0.25$  mm. The test piece shall be straight before it is marked and marking shall be done by fine scribed lines taking care not to cause fracture at the gauge marks. Hold the test piece between the screwed holders in such a way that the load is applied axially. Increase the load as uniformly as possible and measure the maximum load which it can withstand during the test.

## 7.3 Elongation

Put the fractured parts of the test piece carefully so that they fit together, so that they lie in a straight line. Measure the increase in the length of the gauge length and calculate the percentage elongation.

## 8 SAMPLING

### 8.1 Lot

A lot shall consist of all the material from one melt or bar supplied against a single order.

**8.2** Select one percent of spools, but not less than two from each lot. Take specimens sufficiently far

from either end of the spool of wire to be free of kinks, bends or distortion.

## 9 PACKING

The material may be spooled on aluminium spools and should be wound in such a way that it de-spools freely. It should be free of any kinks. A specimen of a spool with typical dimensions is given in Annex A for information.

## 10 MARKING

**10.1** The material shall be marked with the name or trade-mark of the manufacturer, purity of gold, diameter of wire and weight of the contents of the package.

### 10.2 BIS Certification Marking


The product(s) conforming to the requirements of this standard may be certified as per the conformity assessment schemes under the provisions of the *Bureau of Indian Standards Act, 2016* and the Rules and Regulations framed thereunder, and the products may be marked with the Standard Mark.

# ANNEX A

(Clause 9)

## SPECIMEN OF A SPOOL WITH TYPICAL DIMENSIONS

A-1 A sketch of a spool with typical dimensions is given in Fig. 1 for information.

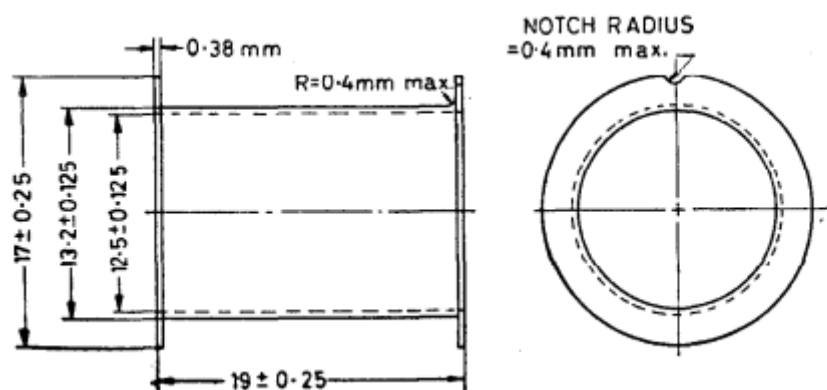

All dimensions in millimetres.

FIG. 1 SKETCH OF THE SPOOL

**ANNEX B***(Foreword)***COMMITTEE COMPOSITION**

Precious Metals Sectional Committee, MTD 10

<i>Organization</i>	<i>Representative(s)</i>
Geological Survey of India, New Delhi	SHRI PARAVJEET SINGH ( <i>Chairperson</i> )
All India Gems and Jewellery Trade Federation, Mumbai	SHRI D. D. KAREL SHRI SURESH I. DHURV ( <i>Alternate</i> )
Association of Gold Refineries and Mints, New Delhi	SHRI ANIL C. KANSARA
Bhartiya Swarnkar Sangh, Jaipur	SHRI DULI CHAND KAREL SHRI PREM KUMAR SONI ( <i>Alternate</i> )
CGR Metalloys Private Limited, Kochi	SHRI JAMES JOSE SHRI JOSEPH K. JAMES ( <i>Alternate</i> )
CSIR - Indian Institute of Toxicology Research, Lucknow	SHRI R. C. MURTHY
CSIR - National Physical Laboratory, New Delhi	DR N. VIJAYAN
CSIR - National Metallurgical Laboratory, Jamshedpur	DR K. K. SAHU DR ASHOK K. MOHANTY ( <i>Alternate</i> )
Consumer Education and Research Centre, Ahmedabad	DR C. J. SHISHOO
Consumer Guidance Society of India, Mumbai	DR SITARAM DIXIT DR M. S. KRAMATH ( <i>Alternate</i> )
Gem and Jewellery Export Promotion Council, Mumbai	SHRI SABYASACHI RAY
Gujarat Gold Centre, Ahmedabad	SHRI SHARAD C. KANSARA
Hindalco Industries Limited, Mumbai	SHRI JAYESH PAWAR SHRI DIVYANG SHAH ( <i>Alternate</i> )
India Government Mint, Mumbai	SHRI BIMAL PARSAD SHRI RAVINDRA GUNDERAO JADHAV ( <i>Alternate</i> )
Indian Association of Hallmarking Centres, New Delhi	SHRI HARSHAD AJMERA SHRI UDAY SHINDE ( <i>Alternate</i> )
Indian Diamond Institute, Surat	SHRI SAMIR D. JOSHI SHRI HITESH VERMA ( <i>Alternate</i> )
Indian Institute of Technology Bombay, Mumbai	SHRI SMRUTIRANJAN PARIDA SHRI N. K. KHOSLA ( <i>Alternate</i> )
Institute of Chemical Technology, Mumbai	DR B. M. BHANAGE SHRI RADHE V. JAYARAM ( <i>Alternate</i> )

<i>Organization</i>	<i>Representative(s)</i>
Jalan and Company, New Delhi	SHRI ISHWAR. JALAN SHRI VINAY JALAN ( <i>Alternate</i> )
MMTC - PAMP India Private Limited, New Delhi	SHRI PANKAJ SHRI ANKUR GOYAL ( <i>Alternate</i> )
National Centre for Compositional Characterization of Materials, New Delhi	DR R. SHEKAR SHRI N. N. MEERVALE ( <i>Alternate</i> )
National Chemical Laboratory, Pune	SHRI C. S. GOPINATH DR E. BALARAMAN ( <i>Alternate</i> )
National Mineral Development Corporation, Hyderabad	DR CH SARVAN KUMAR DR K. SRIRAMGURU ( <i>Alternate</i> )
National Refinery Private Limited, Mumbai	SHRI ASHISH SONEWALA SHRI AMIT J. ( <i>Alternate</i> )
National Test House, Kolkata	DR A. B. MONDAL
Sigma Four, New Delhi	SHRI A. K. BAHL SHRI ANITA BHATIA ( <i>Alternate</i> )
Titan Company Limited, Bengaluru	SHRIMATI MEENAKSHI SUNDARAM SHRI ANIKESH NANDY ( <i>Alternate</i> )
Voluntary Organisation in Interest of Consumer Education (VOICE), New Delhi	SHRI B. K. MUKHOPADHYAY SHRI M. A. U. KHAN ( <i>Alternate</i> )
World Gold Council, New Delhi	SHRI P. R. SOMASUNDARAM
BIS Directorate General	SHRI SANJIV MAINI, SCIENTIST 'F'/SENIOR DIRECTOR AND HEAD (METALLURGICAL ENGINEERING) [REPRESENTING DIRECTOR GENERAL ( <i>Ex-officio</i> )]

*Member Secretary*  
SHRI SHIV PRAKASH  
SCIENTIST 'D'/JOINT DIRECTOR  
(METALLURGICAL ENGINEERING), BIS





## Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 2016* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

### Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Head (Publication & Sales), BIS.

### Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the website- [www.bis.gov.in](http://www.bis.gov.in) or [www.standardsbis.in](http://www.standardsbis.in)

This Indian Standard has been developed from Doc No.: MTD 10 (21753).

### Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

## BUREAU OF INDIAN STANDARDS

### Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002  
Telephones: 2323 0131, 2323 3375, 2323 9402

Website: [www.bis.gov.in](http://www.bis.gov.in)

### Regional Offices:

	Telephones
Central : 601/A, Konnectus Tower -1, 6 <sup>th</sup> Floor, DMRC Building, Bhavbhuti Marg, New Delhi 110002	{ 2323 7617
Eastern : 8 <sup>th</sup> Floor, Plot No 7/7 & 7/8, CP Block, Sector V, Salt Lake, Kolkata, West Bengal 700091	{ 2367 0012 2320 9474
Northern : Plot No. 4-A, Sector 27-B, Madhya Marg, Chandigarh 160019	{ 265 9930
Southern : C.I.T. Campus, IV Cross Road, Taramani, Chennai 600113	{ 2254 1442 2254 1216
Western : Plot No. E-9, Road No.-8, MIDC, Andheri (East), Mumbai 400093	{ 2821 8093

**Branches :** AHMEDABAD. BENGALURU. BHOPAL. BHUBANESHWAR. CHANDIGARH. CHENNAI. COIMBATORE. DEHRADUN. DELHI. FARIDABAD. GHAZIABAD. GUWAHATI. HIMACHAL PRADESH. HUBLI. HYDERABAD. JAIPUR. JAMMU & KASHMIR. JAMSHEDPUR. KOCHI. KOLKATA. LUCKNOW. MADURAI. MUMBAI. NAGPUR. NOIDA. PANIPAT. PATNA. PUNE. RAIPUR. RAJKOT. SURAT. VISAKHAPATNAM.